

SIGRAFLEX®


Flexible graphite foils and sheets for high temperature applications [metric]

SIGRAFLEX products manufactured from expanded natural graphite improve the performance of systems and processes in high temperature applications, minimize energy consumption and guarantee reliability.

SIGRAFLEX flexible graphite foils are free of adhesives and binders. Demonstrating its extraordinary properties, it can be used in ultra high temperature applications ranging up to 3000 °C in inert atmosphere or vacuum. Superior thermal and electrical conductivity makes it a suitable material for a wide range of parts and components in heat treatment furnaces, poly crystalline silicon and semiconductor, solar and other ceramic production equipment. It can be provided in high purity and ultra high purity to prevent product contamination. SIGRAFLEX is often used in combination with SIGRATHERM® soft and rigid felts, SIGRABOND® carbon fiber reinforced carbon and SIGRAFINE® synthetic graphite.

Properties


- Soft and flexible, inert, highly impermeable
- Light weight, simple machining, cutting and punching
- Thermal dissipation, electrically conductive, no static charges
- Excellent chemical resistance
- High purity
- No aging
- No wetting by glass, ceramic or metal melts
- Sheets are available with pinholes for outgassing

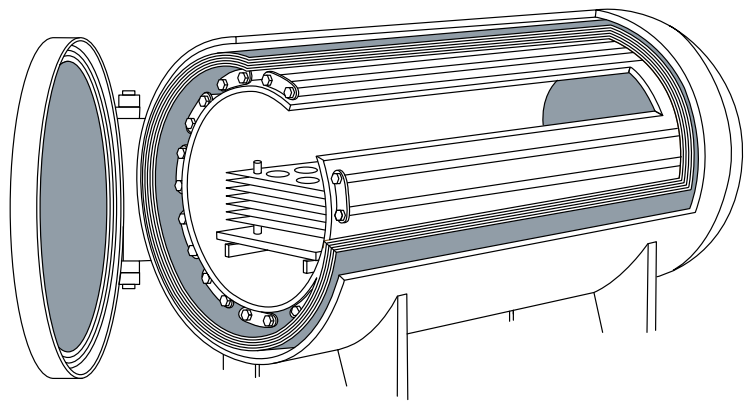


↑ Heat shields – SIGRAFLEX flexible graphite foils and sheets are used as a reflective shield against thermal radiation. Its anisotropic character enhances thermal dissipation and even heat distribution throughout the furnace hot zones.



← Protective liners and diffusion barriers – Off-gas from production parts can build up undesired deposits and dendrites or could corrode or oxidize graphite furnace parts. SIGRAFLEX is used as a protective liner on carbon and graphite components like rigid felt resulting in a longer service life.



← Release liners – A low friction coefficient, being bendable and thermally conductive makes SIGRAFLEX a perfect material for this application. These properties allow high efficiencies and short turnaround times.

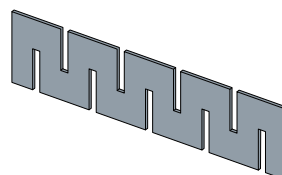


← Heating elements – SIGRAFLEX can also be used as a material to make low cost heating elements, providing a uniform temperature profile.

Material data of SIGRAFLEX® flexible graphite foils and sheets

Typical properties	Units	TH	NH	THP	S	HP	UHP
Standard density	g/cm ³	0.7/1.0/1.2/1.3	0.7/1.0/1.2/1.3	1.0	1.12	1.12	1.12
Ash content [DIN 51903]	%	≤ 0.15	≤ 0.4	≤ 5 or 10 ppm*	≤ 1.0	≤ 0.20	≤ 200 ppm
Carbon content	%	≥ 99.85	≥ 99.6	≥ 99.999 or 99.9995*	≥ 99.0	≥ 99.8	≥ 99.98
Material thickness [supplied as sheets]	mm	1.0/1.5/2.0/3.0	1.0/1.5/2.0/3.0		0.76/1.52/3.05	0.76/1.52/3.05	0.76/1.52/3.05
Material thickness [supplied on rolls]	mm	0.15/0.2/0.25/0.35	0.15/0.2/0.25/0.35	0.25/0.35	0.25/0.51	0.25/0.51	0.25/0.51
Roll width	mm	500/1000	500/1000	500/1000	508/762/1524	508/762/1524	up to 50
Standard roll length	m	50	50	50	96	96	30
Sheet sizes	mm	500 x 1000 1000 x 1000 up to 1500 x 2500	500 x 1000 1000 x 1000 up to 1500 x 2500	500 x 1000 1000 x 1000	up to 1524 x 1524	up to 1524 x 1524	up to 1524 x 1524
Availability		EU grade	EU grade	EU grade	US grade	US grade	US grade

* Ash content ≤ 10 ppm and carbon content ≥ 99.999 % is standard, ≤ 5 ppm and ≥ 99.9995 % on request

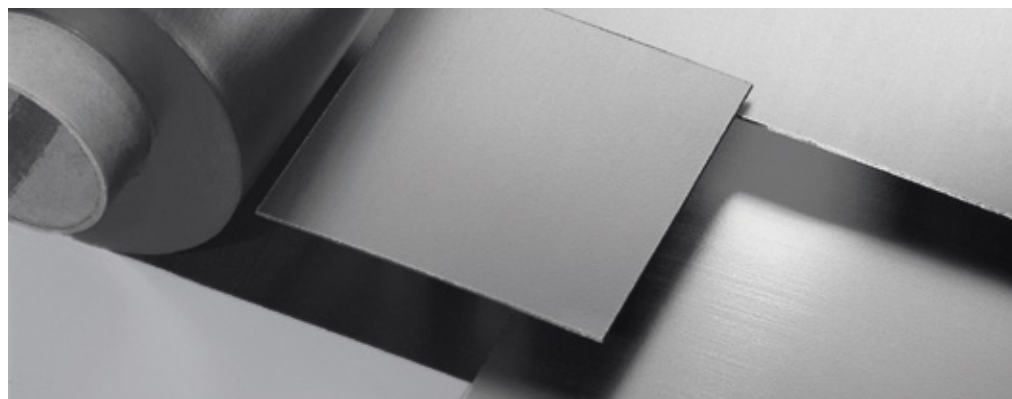

↑ SIGRAFLEX foils and sheets made from expanded natural graphite

Common grades of SIGRAFLEX flexible graphite

Homogenous	TN, NH, HP, S
Postpurified	THP, UHP


Material data of SIGRAFLEX® TH with a density of 1.0 g / cm³

Typical properties	Units	Values
Sublimation temperature	°C	> 3000
Temperature resistance	in air in inert gas and vacuum	approx. 400 approx. 3000
Specific electrical resistivity [20 °C]	parallel to surface perpendicular to surface	11 700
Thermal conductivity [20 °C]	parallel to surface perpendicular to surface	220 5
Specific heat capacity [20 °C]		kJkg ⁻¹ K ⁻¹ 0.7
Thermal expansion coefficient [20 – 1000 °C]	parallel to surface perpendicular to surface	approx. 1 approx. 50
Shore hardness [D]		30
Elongation at break	%	≥ 1
Tensile strength	N/mm ²	≥ 4
Permeability coefficient for air	perpendicular to surface	cm ² /s 2 x 10 ⁻⁵
Coefficient of emission [1500 °C]		0.65
Ash content	%	approx. 0.1


Other values or dimensions on request

Unless stated otherwise, all values are valid at room temperature, typical, non-binding and subject to change. For engineering or design purposes please contact our technical sales team.


Thermal conductivity of SIGRAFLEX with density 1.0 g/cm³ parallel to surface as a function of temperature

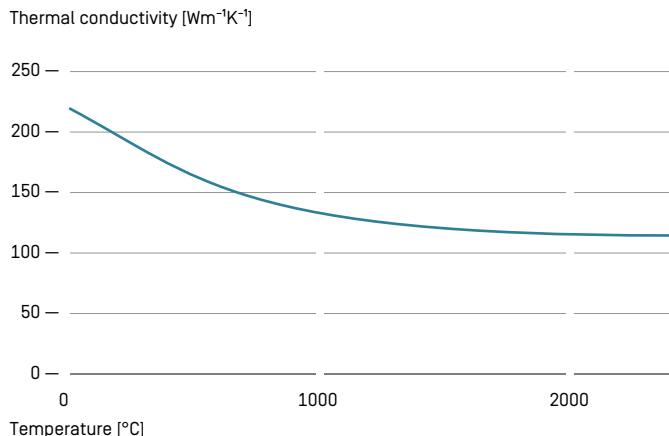


Thermal conductivity of SIGRAFLEX with density 1.0 g/cm³ perpendicular to surface as a function of temperature

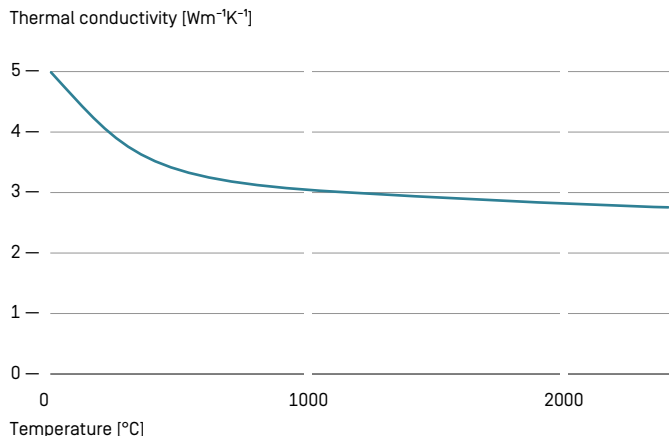


Thermal conductivity of SIGRAFLEX parallel to surface at room temperature as a function of density

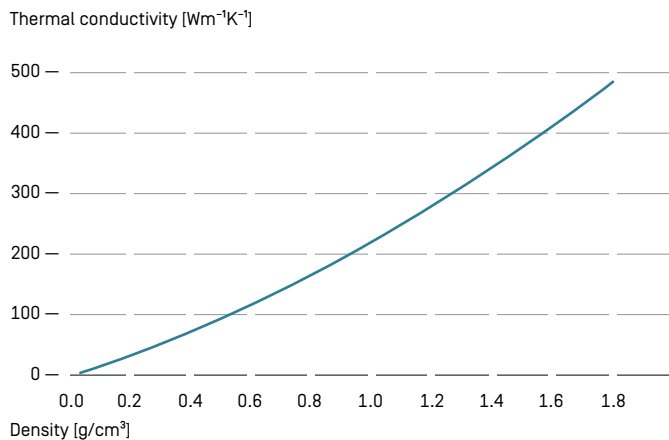


Thermal conductivity of SIGRAFLEX perpendicular to surface at room temperature as a function of density

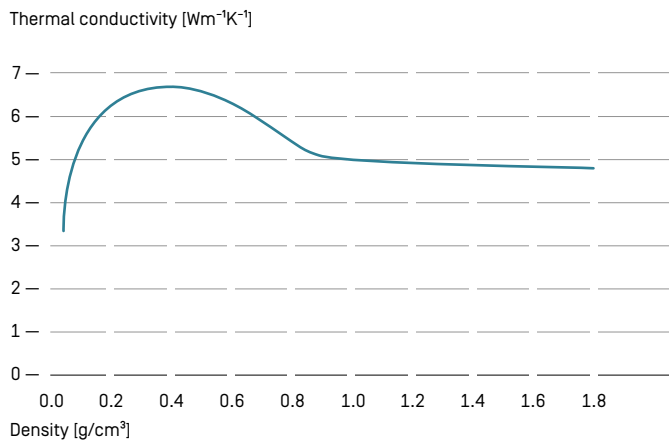


Specific electrical resistivity of SIGRAFLEX parallel to surface at room temperature as a function of density

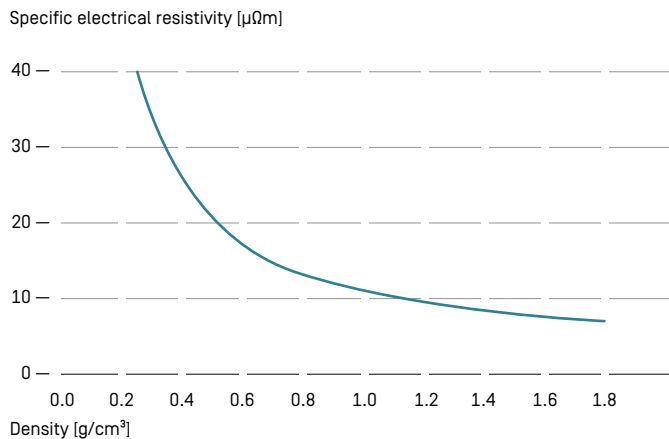

Specific electrical resistivity of SIGRAFLEX with density 1.0 g/cm³ parallel to surface as a function of temperature

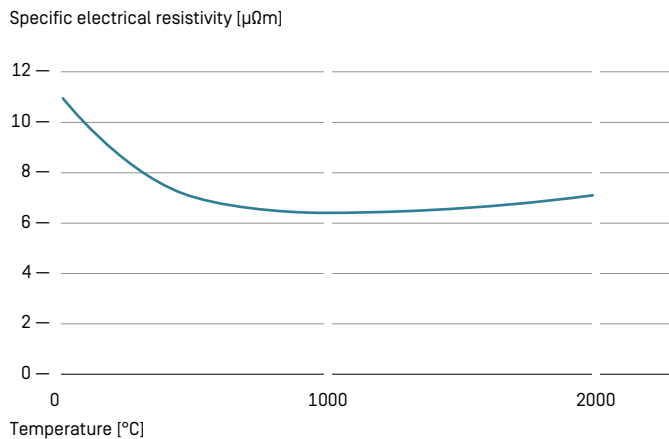

Total emission coefficient of SIGRAFLEX with density 1.0 g/cm³ as a function of temperature

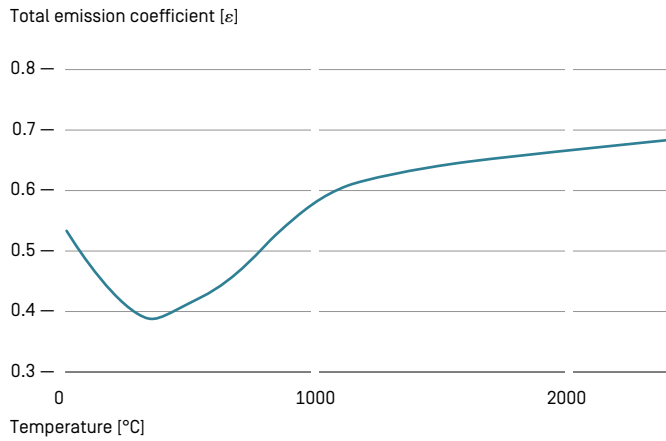

Graphite Solutions | SGL CARBON GmbH | SGL Technic LLC
Sales Europe/Middle East/Africa | sigraflex-europe@sglcarbon.com
Sales Americas | sigraflex-americas@sglcarbon.com
Sales Asia/Pacific | sigraflex-asia@sglcarbon.com
www.sigraflex.com | www.sglcarbon.com

TDS TH_NH_THP_S_HP_UHP_Foil.03
03 2021/0 3NÄ Printed in Germany
®registered trademarks of SGL Carbon SE

This information is based on our present state of knowledge and is intended to provide general notes on our products and their uses. It should therefore not be construed as guaranteeing specific properties of the products described or their suitability for a particular application. Any existing industrial property rights must be observed. The quality of our products is guaranteed under our "General Conditions of Sale".